

# Carbon nanotubes degraded by neutrophil myeloperoxidase induce less pulmonary inflammation

Valerian E. Kagan<sup>1\*</sup>, Nagarjun V. Konduru<sup>1</sup>, Weihong Feng<sup>1</sup>, Brett L. Allen<sup>2</sup>, Jennifer Conroy<sup>3</sup>, Yuri Volkov<sup>3</sup>, Irina I. Vlasova<sup>1</sup>, Natalia A. Belikova<sup>1</sup>, Naveena Yanamala<sup>4</sup>, Alexander Kapralov<sup>1</sup>, Yulia Y. Tyurina<sup>1</sup>, Jingwen Shi<sup>5</sup>, Elena R. Kisin<sup>6</sup>, Ashley R. Murray<sup>6</sup>, Jonathan Franks<sup>7</sup>, Donna Stolz<sup>7</sup>, Pingping Gou<sup>2</sup>, Judith Klein-Seetharaman<sup>4</sup>, Bengt Fadeel<sup>5</sup>, Alexander Star<sup>2</sup> and Anna Shvedova<sup>6</sup>

**We have shown previously that single-walled carbon nanotubes can be catalytically biodegraded over several weeks by the plant-derived enzyme, horseradish peroxidase<sup>1</sup>. However, whether peroxidase intermediates generated inside human cells or biofluids are involved in the biodegradation of carbon nanotubes has not been explored. Here, we show that hypochlorite and reactive radical intermediates of the human neutrophil enzyme myeloperoxidase catalyse the biodegradation of single-walled carbon nanotubes *in vitro*, in neutrophils and to a lesser degree in macrophages. Molecular modelling suggests that interactions of basic amino acids of the enzyme with the carboxyls on the carbon nanotubes position the nanotubes near the catalytic site. Importantly, the biodegraded nanotubes do not generate an inflammatory response when aspirated into the lungs of mice. Our findings suggest that the extent to which carbon nanotubes are biodegraded may be a major determinant of the scale and severity of the associated inflammatory responses in exposed individuals.**

The presence of engineered nanomaterials in technological applications and consumer products has raised concerns about their possible adverse effects on human health and the environment<sup>2</sup>. The unique physicochemical characteristics of carbon nanotubes make their biological effects largely unpredictable<sup>3</sup>. *In vitro* data indicate that single-walled carbon nanotubes may be cytotoxic, largely by inducing oxidative stress<sup>4–6</sup>. Mice exposed to nanotubes by aspiration or inhalation develop a robust pulmonary inflammatory response<sup>7–9</sup>. Inflammation has also been observed when multi-walled carbon nanotubes were injected intraperitoneally in mice<sup>10</sup>.

The chemical degradation of pristine single-walled carbon nanotubes uses strong acids and oxidants (such as mixtures of sulphuric acid and hydrogen peroxide) to modify the surfaces of the nanotubes<sup>11</sup> and to cut them into shorter carboxylated nanotubes. Hypochlorite is also known to generate carboxyl and hydroxyl groups on nanotube surfaces<sup>12,13</sup>, suggesting that strong oxidants may be effective in degrading nanotubes. However, the biodegradation routes of these nanomaterials remain unknown.


Neutrophils kill invading microorganisms by using their oxidant-generating enzymes, such as nicotinamide adenine dinucleotide

phosphate-oxidase (NADPH oxidase), myeloperoxidase and proteases<sup>14</sup>. Human myeloperoxidase (hMPO) generates potent reactive radical intermediates and hypochlorous acid (HOCl), which probably contribute to the degradation of implantable polymeric materials such as poly(ester-urea-urethane)<sup>15</sup>. We reasoned that these same potent hMPO oxidants could also biodegrade nanotubes.

We prepared short carboxylated single-walled carbon nanotubes by chemical cutting<sup>11</sup> (short-cut nanotubes) and used them throughout the study unless specified otherwise. Upon incubation with hMPO and H<sub>2</sub>O<sub>2</sub>, the nanotubes degraded over time, and the suspension turned translucent after 24 h (Fig. 1a). Neither hMPO alone nor H<sub>2</sub>O<sub>2</sub> alone caused nanotube degradation. Incubation of hMPO with nanotubes alone, without H<sub>2</sub>O<sub>2</sub>, did not inactivate the enzyme (Supplementary Fig. S1a). In the presence of H<sub>2</sub>O<sub>2</sub>, however, hMPO retained 50% of its activity over 2.5 h but decayed after 5 h (Supplementary Fig. S1b). We therefore added fresh hMPO and H<sub>2</sub>O<sub>2</sub> to the nanotube suspensions every 5 h.


Dynamic light scattering of nanotubes treated with hMPO and H<sub>2</sub>O<sub>2</sub> showed several peaks that corresponded with a reduction in the size of the treated nanotubes compared to untreated controls (Fig. 1b). Native agarose gel electrophoresis showed that the majority of non-degraded carbon nanotubes remained as a dark congested band in the loading well or migrated as a smear in the presence of albumin/bromophenol blue. In contrast, no detectable bands were found on native gels when biodegraded carbon nanotubes were electrophoresed under similar conditions (Supplementary Fig. S1d). Furthermore, visible–near infrared (vis–NIR) absorbance spectra of treated nanotubes showed that the characteristic metallic band (M1) and semiconducting (S2) transition band were suppressed during incubation (Fig. 1c). The disorder-induced D-band at ~1,250–1,350 cm<sup>–1</sup> increased in the Raman spectra, whereas the tangential-mode G-band decreased with incubation time, suggesting that the graphene sidewall was oxidized (Fig. 1d). Drastic changes in nanotube morphology were further confirmed by transmission (TEM) and scanning electron microscopy (SEM). The characteristic fibrillar structure of intact nanotubes was completely lost, and the bulk of the nanotubes was no longer present after 24 h of incubation (Fig. 1e,f). Only a few

<sup>1</sup>Department of Environmental and Occupational Health, Center for Free Radical and Antioxidant Health, Graduate School of Public Health, University of Pittsburgh, Pittsburgh, Pennsylvania, USA, <sup>2</sup>Department of Chemistry, University of Pittsburgh, Pittsburgh, Pennsylvania, USA, <sup>3</sup>Department of Clinical Medicine and Centre for Research on Adaptive Nanostructures and Nanodevices (CRANN), Trinity College Dublin, Dublin, Ireland, <sup>4</sup>Department of Structural Biology, University of Pittsburgh, Pittsburgh, Pennsylvania, USA, <sup>5</sup>Division of Molecular Toxicology, Institute of Environmental Medicine, Karolinska Institutet, Stockholm, Sweden, <sup>6</sup>Pathology and Physiology Research Branch, Health Effects Laboratory Division (HELD), National Institute for Occupational Safety and Health (NIOSH) and Department of Physiology and Pharmacology, West Virginia University, Morgantown, West Virginia, USA, <sup>7</sup>Department of Cell Biology and Physiology, University of Pittsburgh, Pittsburgh, Pennsylvania, USA. \*e-mail: kagan@pitt.edu

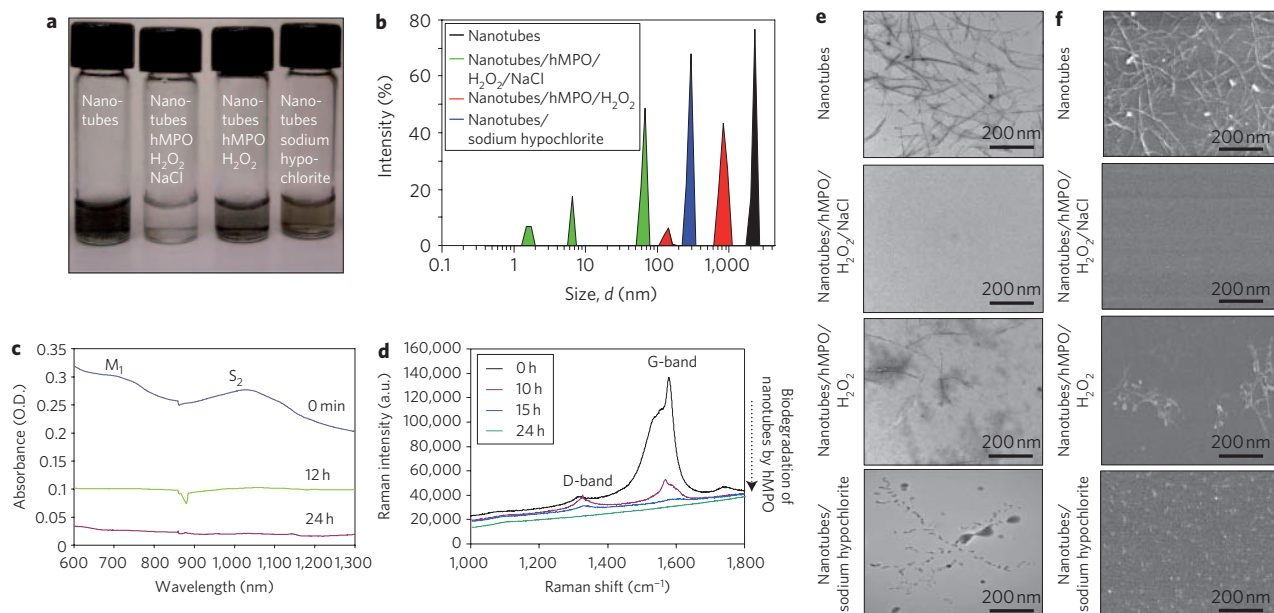


**Figure 1 | Spectroscopic and electron microscopic evaluation of human myeloperoxidase (hMPO)-mediated degradation of nanotubes *in vitro*.**

**a**, Photograph of different short-cut nanotube suspensions after 24 h. **b**, Dynamic light scattering showing multiple smaller peaks corresponding to biodegraded nanotubes. **c**, Infrared spectra showing loss of M1 and S2 bands as nanotubes are degraded in the presence of hMPO and H<sub>2</sub>O<sub>2</sub>. **d**, Raman spectra (excitation, 633 nm) of ethanol-dried nanotubes (black) and (hMPO and H<sub>2</sub>O<sub>2</sub>)-treated nanotubes, showing loss of the characteristic G-band, followed by appearance and decay of the D-band over time. **e,f**, TEM (**e**) and SEM (**f**) analyses, tracking the biodegradation of nanotubes after 24 h.

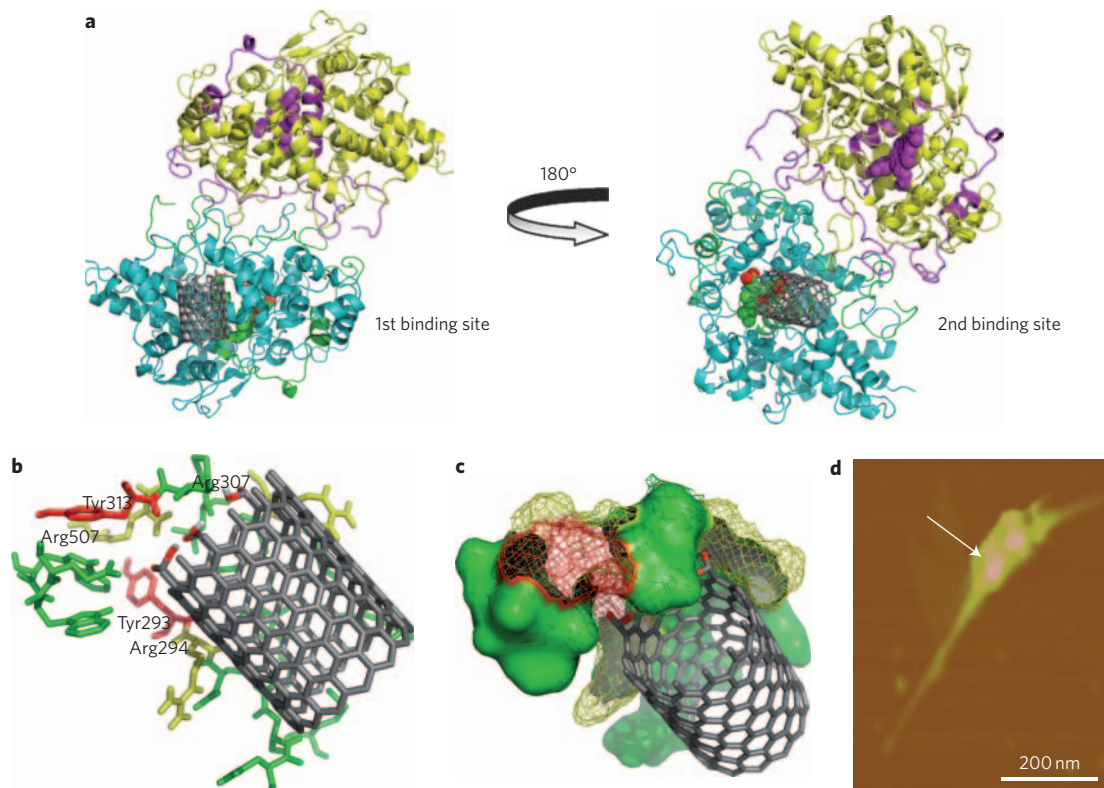


**Figure 2 | Molecular modelling, demonstrating possible nanotube interaction sites on hMPO. a**, Two putative binding sites for nanotubes on the hMPO monomer surface are located on each side of the protein. The best model site with lowest binding energy is shown for carboxylated short-cut nanotubes (left) and pristine nanotubes (right). **b**, Stabilization of the carboxylated ends of the nanotubes by arginine (yellow) and tyrosine residues (red) in hMPO in the first binding pocket (left). All residues shown are within 5 Å of nanotubes and are predicted to participate in the degradative catalysis of nanotubes. This includes Tyr293, Arg294, Arg307, Tyr313 and Arg507. **c**, As **b**, using space-fill representation. **d**, AFM image confirming the binding of a dimer of hMPO with a single nanotube.

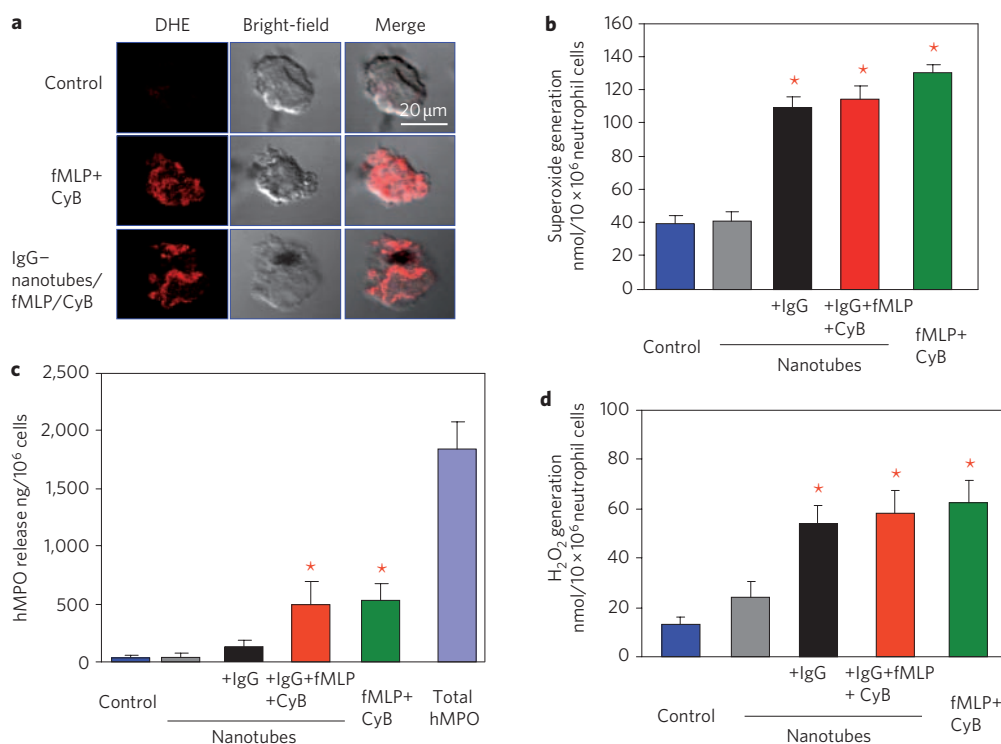

**Figure 3 | IgG-functionalized nanotubes induce the release of hMPO and the generation of reactive oxygen species in human peripheral blood**

**neutrophils.** **a**, Assessments of intracellular superoxide in neutrophils treated with fMLP and cytochalasin B (CyB) alone or plus IgG-nanotubes for 30 min at 37 °C. Representative confocal micrographs of neutrophils stained with dihydroethidium (DHE) to detect superoxide generation are shown. **b**, Quantitative assessment of extracellular generation of superoxide radicals. **c**, Extracellular release of hMPO in response to fMLP, cytochalasin B and IgG-nanotubes. **d**, Generation of extracellular  $H_2O_2$  30 min after challenge with nanotubes assessed by the Amplex red assay. Data shown in panels **b–d** are from three independent experiments performed with neutrophils obtained from different donors and are expressed as mean values  $\pm$  s.d. (\* $P < 0.05$ , groups versus control).

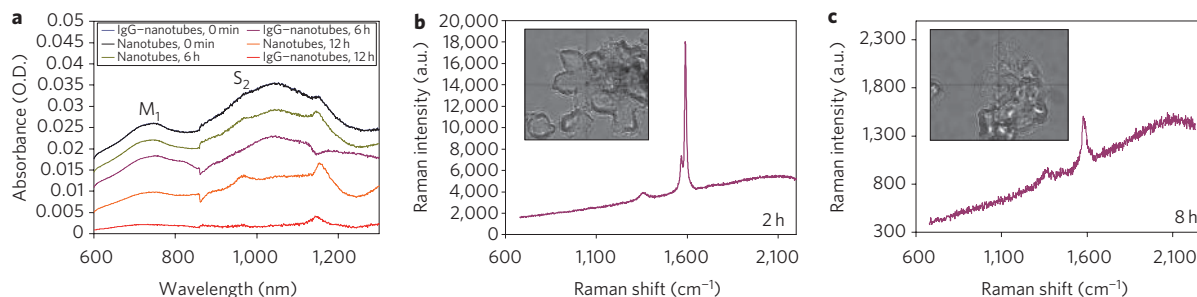


**Figure 4 | Biodegradation of nanotubes in neutrophils evaluated by infrared and Raman spectroscopy.** **a**, Vis-NIR spectra showing biodegradation of nanotubes and IgG-nanotubes by human neutrophils after 0, 6 and 12 h. **b,c**, Raman spectra (excitation, 473 nm) recorded from different areas of neutrophils containing IgG-nanotubes at 2 h (**b**) and 8 h (**c**). Inset shows bright-field image of the neutrophils with engulfed IgG-nanotubes. The Raman spectra (red lines) with their corresponding G- and D-bands recorded from different areas of neutrophils are indicated by the cross-wire on the bright-field images.

1 visual fields showed evidence of residual carbonaceous material  
2 (Supplementary Fig. S1c).

3 After 12 h of incubation of the nanotubes with hMPO and  $H_2O_2$ ,  
4 gas chromatography–mass spectrometry (GC–MS) revealed several  
5 major products, including short-chain tri-carboxylated alkanes and  
6 alkenes, and molecular ions of di-carboxylated short-chain and  
7 mono-carboxylated products (Supplementary Fig. S2). Analysis of  
8 the products extracted from fully biodegraded nanotubes demonstrated  
9 the presence of short-chain carboxylated alkanes and alkenes (data not  
10 shown). These results are in agreement with previous studies showing  
11 carboxylation of nanotubes upon acid treatment<sup>16</sup>. Furthermore, a 60%  
12 increase in  $CO_2$  levels was detected in biodegraded nanotubes compared  
13 to nanotubes incubated with hMPO alone or  $H_2O_2$  alone.

Reactive radical intermediates of hMPO and hypochlorite  
could be two oxidants involved in nanotube biodegradation<sup>17</sup>.  
Both are formed when hMPO is incubated with  $H_2O_2$  in the presence  
of sodium chloride (NaCl), whereas only peroxidase reactive  
radical intermediates are generated in the absence of NaCl.  
Biodegradation of nanotubes occurred during their incubation with  
hMPO and  $H_2O_2$  in the absence of NaCl, although it was markedly  
suppressed compared to results obtained for incubation with hMPO  
and  $H_2O_2$  plus NaCl (Supplementary Fig. S3). Accordingly, when  
nanotubes were exposed to sodium hypochlorite alone, the degradation  
process was markedly attenuated (Fig. 1a,b,e,f), suggesting a  
radical-driven mechanism. Taurine, a scavenger of HOCl (ref. 18),  
also impeded the biodegradation of nanotubes. The effect was



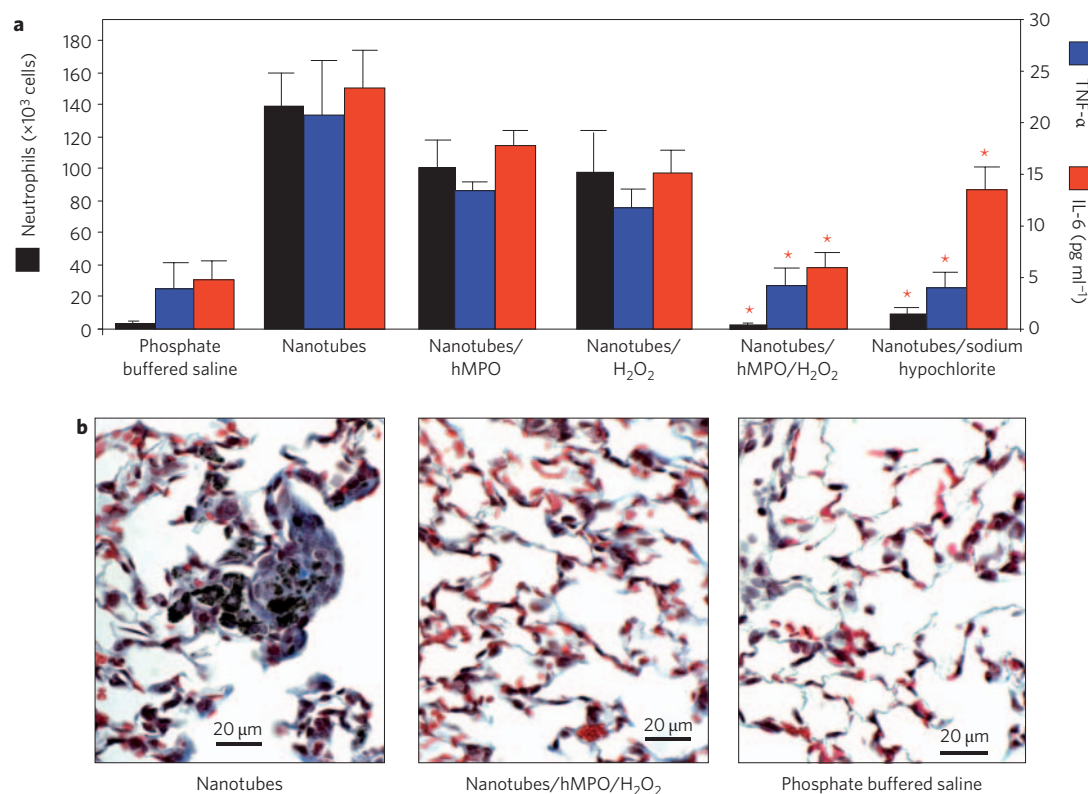

**Figure 5 | Biodegraded nanotubes do not elicit a pro-inflammatory pulmonary response in C57BL/6 mice.** **a**, Neutrophil counts and expression of TNF- $\alpha$  (blue) and IL-6 (red) in bronchoalveolar lavage fluid were measured 24 h after exposure to the indicated treatments by means of pharyngeal aspiration. Data represent mean values  $\pm$  s.e. ( $n = 6$  mice per group). \* $P < 0.05$  groups versus nanotubes alone. **b**, Representative images of lung sections from mice exposed to 40  $\mu$ g/animal nanotubes, showing granuloma formation on day 7 after pharyngeal aspiration. Similar to the results from control animals exposed to phosphate buffered saline, no granuloma formation is seen in the lungs of mice exposed to degraded nanotubes. Biodegradation of nanotubes was induced by their incubation with hMPO and H $_2$ O $_2$ .

1 similar to that achieved in a NaCl-free medium (Supplementary  
2 Fig. S3). Overall, these data imply that both the peroxidase reactive  
3 intermediates and hypochlorite contributed to biodegradation.

4 hMPO is known to avidly bind to negatively charged molecules,  
5 including an anionic phospholipid, phosphatidylserine (PS; ref. 19).  
6 PS-coated nanotubes showed biodegradation by hMPO,  
7 whereas nanotubes coated with non-charged phosphatidylcholine—  
8 a major lung surfactant phospholipid—were not biodegraded  
9 (Supplementary Fig. S4). To better understand the role of surface  
10 charges on short-cut nanotubes in the interactions with hMPO, we  
11 used molecular modelling. The simulations revealed two potential  
12 interaction sites between hMPO and the nanotubes. One site was  
13 located at the proximal end of the haem group, involving tyrosine resi-  
14 dues 293 and 313 (known to be catalytically active in hMPO<sup>20</sup>; Fig. 2a,  
15 left). The simulation pointed to a strong interaction of positively  
16 charged residues on hMPO (Supplementary Table S1) with the  
17 carboxyl surface of the nanotubes, in line with studies performed by  
18 Kam and colleagues<sup>21</sup> on nanotube interactions with other proteins.  
19 We thus propose a site-localized reaction in which hMPO positive  
20 charges favour the binding of nanotubes, and radical-supporting  
21 aromatic groups participate in the cleavage of the nanotubes  
22 (Supplementary Fig. S5). Atomic force microscopy demonstrated  
23 the attachment of hMPO to the surface of the nanotubes (Fig. 2d;  
24 Supplementary Fig. S6).

25 The second binding site close to the distal end of the haem group,  
26 far away from catalytically competent tyrosine residues 293 and 313  
27 (Fig. 2a, right), may be involved in the binding of pristine (non-car-  
28 boxylated) nanotubes. Notably, pristine nanotubes underwent less  
29 effective biodegradation by hMPO both in the presence and

30 absence of NaCl (Supplementary Fig. S7). Pristine nanotubes have  
31 been shown to be susceptible to HOCl oxidation<sup>13</sup>. In line with  
32 this, our Raman spectroscopy data confirmed that the oxidation  
33 of pristine nanotubes is mediated by hypochlorite (Supplementary  
34 Fig. S8). Interestingly, the short-cut nanotubes were equally suscep-  
35 tible to oxidation, indicating a random reaction of hypochlorite with  
36 both types of nanotubes. It is tempting to speculate that HOCl  
37 might be essential for triggering and initially accumulating carboxy-  
38 lated sites on pristine nanotubes, which leads to the better position-  
39 ing of hMPO and subsequent biodegradation of the tubes by  
40 reactive intermediates of the enzyme (Fig. 2).

41 We next evaluated whether oxidative biodegradation of nanotubes  
42 can be executed by hMPO-rich human neutrophils. Stimulation of neu-  
43 trophils was performed using a chemoattractant, *N*-formyl-methionyl-  
44 leucyl-phenylalanine (fMLP), in combination with a degranulation  
45 promoting agent, cytochalasin B. Cytochalasin B is known to increase  
46 the activity of hMPO and trigger its release<sup>22</sup>. During neutrophil acti-  
47 vation, hMPO is translocated into phagosomes, in which the fully  
48 assembled, membrane-bound NADPH oxidase generates superoxide  
49 radicals<sup>14</sup>. The latter dismutates to H $_2$ O $_2$ , which enables hMPO to  
50 produce reactive intermediates and HOCl. Dihydroethidium staining  
51 and cytochrome-c reduction assay confirmed the activation of neutro-  
52 phils upon stimulation with fMLP and cytochalasin B (Fig. 3a,b).  
53 Because 75% of the total hMPO remained inside the cells (Fig. 3c),  
54 we targeted nanotubes to neutrophils by using IgG functionalization<sup>23</sup>.  
55 Using fluorescently labelled nanotubes, we found a significant increase  
56 in the uptake of IgG-nanotubes by neutrophils compared to that of  
57 non-functionalized nanotubes (Supplementary Fig. S9a,b).  
58 Furthermore, we observed sustained basal generation of oxidants (for

up to 12 h) by neutrophils incubated with IgG–nanotubes as assessed by 2',7'-dichlorofluorescein-di-acetate and Amplex Red assays (Fig. 3d; Supplementary Fig. S10).

Under these conditions, IgG–nanotubes underwent 100% degradation, whereas only 30% of non-IgG-functionalized nanotubes were degraded in neutrophil suspensions, as was made evident by infrared spectroscopy (Fig. 4a). Inhibitors of hMPO (4-aminobenzoic acid hydrazide)<sup>24</sup> and NADPH oxidase (apocynin)<sup>25</sup> attenuated the degradation process (Supplementary Fig. S11). This finding suggests that both hMPO and NADPH oxidase were essential for nanotube biodegradation by neutrophils. Raman microscopy of IgG-functionalized nanotubes inside neutrophils showed a marked loss of the G-band and appearance of a strong D-band. This is characteristic of oxidatively modified nanotubes (Fig. 4b,c) and demonstrates that the uptake of IgG-functionalized nanotubes by neutrophils resulted in an hMPO-driven biodegradation process in activated cells.

Human monocyte derived macrophages are known to contain lower levels of hMPO than neutrophils (13 ng hMPO per 10<sup>6</sup> macrophages, compared with 1.8 µg hMPO per 10<sup>6</sup> neutrophils). Infrared spectroscopic assessments revealed only negligible degradation of IgG–nanotubes by macrophages after 6 h of incubation and 13% degradation at 12 h (compared with 30% and 100% biodegradation of IgG–nanotubes by neutrophils at 6 and 12 h, respectively; Supplementary Fig. S11). More pronounced (~50%) biodegradation of IgG–nanotubes by macrophages occurred only after 48 h. As described previously<sup>26,27</sup>, these results suggest that hMPO activity is an important determinant of the biodegradation of nanotubes as well as other nanoformulations.

Pharyngeal aspiration or inhalation of nanotubes is known to induce a robust pulmonary inflammatory response in mice, with early onset of fibrosis<sup>7,8</sup>. To address whether the biodegradation process would render nanotubes non-inflammatory, we assessed the amounts of neutrophils and the levels of cytokines in bronchoalveolar lavage obtained from mice at day 1 (Fig. 5a) and day 7 (Supplementary Fig. S12) after nanotube exposure. The profiles of these inflammation markers in animals exposed to biodegraded nanotubes by pharyngeal aspiration were essentially indistinguishable from control values. In contrast, non-degraded short-cut nanotubes elicited an acute inflammatory response. Similar responses were seen with nanotubes pre-incubated with either hMPO or H<sub>2</sub>O<sub>2</sub> alone (Fig. 5a). Non-degraded nanotubes also induced the formation of tissue granulomas, but no granulomas were observed in the lungs of mice exposed to biodegraded nanotubes (Fig. 5b).

Partially degraded nanotubes obtained after 12 h of incubation with hMPO and H<sub>2</sub>O<sub>2</sub> still retained some of their characteristic morphologic and spectral features, and induced less inflammatory responses in mice than the non-biodegraded nanotubes (Supplementary Fig. S13). Thus, hMPO-mediated biodegradation of nanotubes serves to mitigate the pro-inflammatory potential of these nanomaterials.

To summarize, we have shown a novel route of enzymatic biodegradation of single-walled carbon nanotubes relevant to potential respiratory exposures during the production and handling of carbon nanotubes. Based on these findings, strategies for mitigating the pro-inflammatory effects of these nanomaterials in the occupational setting may be developed. Pulmonary inflammation following carbon nanotube exposures in mice<sup>7–9</sup> could be explained by the ineffective internalization of non-functionalized nanotubes by phagocytic cells<sup>28</sup>. Moreover, it is possible that the doses of nanotubes commonly used in toxicological studies may overwhelm the biodegradation capacity of the neutrophil enzymatic system. Nonetheless, the propensity of nanotubes to undergo hMPO-mediated biodegradation suggests that these nanomaterials may be considered as tools for delivery of therapeutic agents in biomedical applications when used at appropriate and readily degradable concentrations.

## Methods

**Chemical degradation of nanotubes.** Mixtures contained 30 µg hMPO with an activity of 1.1 U µg<sup>-1</sup> (Sigma) per 300 µg of nanotubes suspended in 300 µl of 50 mM phosphate buffer containing 140 mM NaCl and 100 µM diethylene triamine pentaacetic acid (DTPA), a transition metal chelator. Hydrogen peroxide was added at a rate of 200 µM per hour for 5 h. Because of loss of activity of hMPO in the incubation system, the enzyme was replenished after 5 h and the reaction mixture was maintained at 37 °C for 24 h. Where indicated, sodium hypochlorite was added every hour to give concentrations of 200 µM for 24 h at 37 °C.

**Computational modelling.** The three-dimensional structures of nanotubes were generated using Nanotube Modeller software (<http://www.jcrystal.com/products/wincnt/index.htm>). The diameter was set at 1.1 nm using chirality parameters *m* and *n* of 14 and 0. For carboxylated nanotubes, one of the ends of the nanotube was carboxylated using the Builder tool, provided by Pymol<sup>29</sup> visualization software. Nanotubes were docked to the hMPO X-ray crystal structure (PDB ID: 1CXP, chains A & C), using the Lamarckian Genetic Algorithm provided by AutoDock4.0 software, as described previously<sup>30</sup> with the following modifications. The entire surface of the target was searched for possible binding sites without bias. The grid maps representing the protein were calculated using the AutoGrid option. A cubic box was built around the protein with 126 × 126 × 126 points. A spacing of 0.41 Å between the grid points was used, placing the centre of the protein at the centre of the cube. Docking simulations were carried out with an initial population of 300 structures, and a maximum number of 50,000,000 energy evaluations. The resulting top 25 minimum energy orientations with ≤2.0 Å r.m.s. deviation were clustered. AutoDock4.0 software was run using distributed computing ([www.pittgrid.pitt.edu](http://www.pittgrid.pitt.edu)).

**Functionalized nanotubes with IgG.** Nanotubes (200 µg) in HEPES buffer (pH 7.4) were incubated with purified human IgG (Invitrogen) in 1:1 ratio (w/w) for 48 h at 37 °C with sonication for 10 min every 5 h in a water bath sonicator.

**Raman microscopy of nanotubes in neutrophils.** Cells incubated with IgG–nanotubes were fixed using 2.5% paraformaldehyde and cyto-spun onto 1.5-mm-thick cover glass (Fisher Scientific). An NTEGRA SPECTRA AFM–Raman microscope (NT-MDT) was used with a cobalt solid-state laser operating at a wavelength of 473 nm. All Raman spectra were recorded for 2 s, at 10% laser power, using a ×100 oil immersion objective. For each spectrum a static grating (2,400 l mm<sup>-1</sup>) scan was taken over the range 678.28–2,231.82 cm<sup>-1</sup>. Detection of the Raman scattered light was performed using a Peltier cooled charge-coupled device detector. From each of the samples an average of 20 spectra was recorded.

**hMPO contents in cells and its release.** Levels of hMPO in cells were determined by ELISA kit (Alpco Diagnostics) after 30 min incubation with either fMLP with cytochalasin B or nanotubes. Neutrophils were centrifuged at 1,000g for 10 min. The supernatant and pellet were obtained and used separately for hMPO measurements according to the manufacturer's manual. The amounts of hMPO were expressed as ng/10<sup>6</sup> cells.

**Infrared spectroscopy of nanotubes in neutrophils.** Neutrophils incubated with IgG–nanotubes were harvested from culture plates after 24 h of incubation together with the incubation medium. The cell suspensions were further subjected to harsh sonication for 1 h using the ultrasonic probe tip sonicator (Cole-Palmer Ultrasonic Homogenizer, 20 kHz), and the spectra were then recorded in the samples using a vis–NIR spectrophotometer (Perkin-Elmer).

**Particulate instillation.** Pharyngeal aspiration was used for particulate administration to C57BL/6 mice. Briefly, after anaesthetization with ketamine and xylazine anesthesia (62.5 and 2.5 mg kg<sup>-1</sup>, respectively), the mouse was placed on a board in a near-vertical position. The animal's tongue was extended with lined forceps, and a suspension of particulates (50 µl, non-biodegraded and biodegraded nanotubes at a dose of 40 µg/mouse each) was placed in the posterior of pharynx. The tongue was held until the suspension was aspirated into the lungs. All mice in particle and phosphate buffered saline control groups survived this exposure procedure. This technique provides a good distribution of particles, widely disseminated in a peri-bronchiolar pattern within the alveolar region. Animals treated with the particulates recovered easily after anaesthesia with no behavioural or negative health outcomes.

Received 10 September 2009; accepted 17 February 2010;  
published online XX XX 2010

## References

- Allen, B. L. *et al.* Biodegradation of single-walled carbon nanotubes through enzymatic catalysis. *Nano Lett.* **8**, 3899–3903 (2008).
- Maynard, A. D. *et al.* Safe handling of nanotechnology. *Nature* **444**, 267–269 (2006).
- Shvedova, A. A. *et al.* Mechanisms of pulmonary toxicity and medical applications of carbon nanotubes: two faces of Janus? *Pharmacol. Ther.* **121**, 192–204 (2009).

- 1 4. Jia, G. *et al.* Cytotoxicity of carbon nanomaterials: single-wall nanotube,  
2 multi-wall nanotube and fullerene. *Environ. Sci. Technol.* **39**, 1378–1383 (2005).
- 3 5. Kagan, V. E. *et al.* Direct and indirect effects of single walled carbon nanotubes  
4 on RAW 264.7 macrophages: role of iron. *Toxicol. Lett.* **165**, 88–100 (2006).
- 5 6. Kisin, E. R. *et al.* Single-walled carbon nanotubes: geno- and cytotoxic effects in  
6 lung fibroblast V79 cells. *J. Toxicol. Environ. Health. A* **70**, 2071–2079 (2007).
- 7 7. Shvedova, A. A. *et al.* Unusual inflammatory and fibrogenic pulmonary  
8 responses to single-walled carbon nanotubes in mice. *Am. J. Physiol. Lung Cell.*  
9 *Mol. Physiol.* **289**, L698–L708 (2005).
- 10 8. Shvedova, A. A. *et al.* Inhalation vs. aspiration of single-walled carbon nanotubes  
11 in C57BL/6 mice: inflammation, fibrosis, oxidative stress and mutagenesis.  
12 *Am. J. Physiol. Lung Cell. Mol. Physiol.* **295**, L552–L565 (2008).
- 13 9. Muller, J. *et al.* Structural defects play a major role in the acute lung toxicity of  
14 multiwall carbon nanotubes: toxicological aspects. *Chem. Res. Toxicol.* **21**,  
15 1698–1705 (2008).
- 16 10. Poland, C. A. *et al.* Carbon nanotubes introduced into the abdominal cavity of  
17 mice show asbestos-like pathogenicity in a pilot study. *Nature Nanotech.* **3**,  
18 423–428 (2008).
- 19 11. Wei, Z., Kondratenko, M., Dao, L. H. & Perepichka, D. F. Rectifying diodes from  
20 asymmetrically functionalized single-wall carbon nanotubes. *J. Am. Chem. Soc.*  
21 **128**, 3134–3135 (2006).
- 22 12. Yoon, S. M. *et al.* Selective oxidation on metallic carbon nanotubes by halogen  
23 oxoanions. *J. Am. Chem. Soc.* **130**, 2610–2616 (2008).
- 24 13. Wu, C.-H. Studies of the equilibrium and thermodynamics of the absorption of  
25 Cu<sup>2+</sup> onto as-produced and modified carbon nanotubes. *J. Colloid Interface Sci.*  
26 **311**, 338–346 (2007).
- 27 14. Hampton, M. B., Kettle, A. J. & Winterbourn, C. C. Inside the neutrophil  
28 phagosome: oxidants, myeloperoxidase and bacterial killing. *Blood* **92**,  
29 3007–3017 (1998).
- 30 15. Sutherland, K., Mahoney, J. R., II, Coury, A. J. & Eaton, J. W. Degradation of  
31 biomaterials by phagocyte-derived oxidants. *J. Clin. Invest.* **92**,  
32 2360–2367 (1993).
- 33 16. Kuznetsova, A. *et al.* Oxygen-containing functional groups on single-wall  
34 carbon nanotubes: NEXAFS and vibrational spectroscopic studies. *J. Am. Chem.*  
35 *Soc.* **123**, 10699–10704 (2001).
- 36 17. Panasenko, O. M. *et al.* Generation of free radicals during decomposition of  
37 hydroperoxide in the presence of myeloperoxidase or activated neutrophils.  
38 *Biochemistry (Mosc)* **70**, 998–1004 (2005).
- 39 18. Kearns, S. & Dawson, R., Jr. Cytoprotective effect of taurine against  
40 hypochlorous acid toxicity to PC12 cells. *Adv. Exp. Med. Biol.* **483**,  
41 563–570 (2000).
- 42 19. Lessig, J. *et al.* Myeloperoxidase binds to non-vital spermatozoa on  
43 phosphatidylserine epitopes. *Apoptosis* **12**, 1803–1812 (2007).
- 44 20. Olivier, M. L. & Paul, R. O. EPR spin-trapping of a myeloperoxidase protein  
45 radical. *Biochem. Biophys. Res. Commun.* **1**, 199–202 (2000).
- 46 21. Kam, N. & Dai, H. Single walled carbon nanotubes for transport and delivery of  
47 biological cargos. *Phys. Stat. Sol.* **243**, 3561–3566 (2006).
- 48 22. Zipfel, M., Carmine, T. C., Gerber, C., Niethammer, D. & Bruchelt, G. Evidence  
49 for the activation of myeloperoxidase by f-Meth-Leu-Phe prior to its release  
50 from neutrophil granulocytes. *Biochem. Biophys. Res. Commun.* **232**,  
51 209–212 (1997).
- 52 23. McKenzie, S. E. & Schreiber, A. D. Fc gamma receptors in phagocytes. *Curr.*  
53 *Opin. Hematol.* **5**, 16–21 (1998).
- 54 24. Kettle, A. J., Gedy, C. A. & Winterbourn, C. C. Mechanism of inactivation of  
55 myeloperoxidase by 4-aminobenzoic acid hydrazide. *Biochem. J.* **321**,  
56 503–508 (1997).
- 57 25. Touyz, R. M. Apocynin, NADPH oxidase and vascular cells: a complex matter.  
58 *Hypertension* **51**, 172–174 (2008).
- 59 26. Batrakova, E. V. *et al.* A macrophage–nanozyme delivery system for Parkinson's  
60 disease. *Bioconjug. Chem.* **18**, 1498–1506 (2007).
- 61 27. Dou, H. *et al.* Development of a macrophage-based nanoparticle platform for  
62 antiretroviral drug delivery. *Blood* **108**, 2827–2835 (2006).
- 63 28. Konduru, N. V. *et al.* Phosphatidylserine targets single-walled carbon nanotubes  
64 to professional phagocytes *in vitro* and *in vivo*. *PLoS One* **4**, e4398 (2009).
- 65 29. DeLano, W. L. *The PyMOL Molecular Graphics System* (DeLano  
66 Scientific, 2002).
- 67 30. Yanamala, N., Tirupula, K. C. & Klein-Seetharaman, J. Preferential binding of  
68 allosteric modulators to active and inactive conformational states of  
69 metabotropic glutamate receptors. *BMC Bioinformatics* **9**(Suppl 1), S16 (2008).

## Acknowledgements

This work was supported by NIOSH OH008282, NIH HL70755, HL094488, NLM LM007994-05, NORA 927000Y, NORA 927Z1LU, NTRC 927ZJHE, NSF CAREER 0449117, AFOSR FA 9550-09-1-0478, 7th Framework Program of the European Commission (EC-FP7-NANOMMUNE- 214281) and by the Science Foundation of Ireland (SRC BioNanoInteract and CRANN), HEA and PRTL. The authors would like to thank M. Bruchez for assistance with dynamic light scattering experiments.

## Disclaimer

The findings and conclusions in this report are those of the authors and do not necessarily represent the views of the National Institute for Occupational Safety and Health.

## Author contributions

V.E.K., N.V.K., B.F. and A.S. designed the experiments, analysed the data and wrote the manuscript. W.F., J.S. and N.V.K. performed the neutrophil-based experiments. B.L.A. and N.V.K. participated in spectroscopic studies. I.I.V. and A.K. performed ESR measurements and gel electrophoresis. E.R.K., A.R.M. and A.S. designed and performed the animal experiments and evaluated the data. N.Y. and J.K.S. performed the molecular modelling studies. J.F. and D.S. carried out the electron microscopic studies. P.G. synthesized fluorescence labelled nanotubes. J.C. and Y.V. carried out the Raman microscopic studies. N.A.B. and Y.Y.T. performed the mass spectrometric analysis. All co-authors discussed the results and approved the final version of the manuscript.

## Additional information

The authors declare no competing financial interests. Supplementary information accompanies this paper at [www.nature.com/naturenanotechnology](http://www.nature.com/naturenanotechnology). Reprints and permission information is available online at <http://npg.nature.com/reprintsandpermissions/>. Correspondence and requests for materials should be addressed to V.E.K.

Publisher: Nature

Journal: Nature Nanotechnology

Article number: nnano.2010.44

Author (s): Kagan *et al.*

Title of paper: Carbon nanotubes degraded by neutrophil myeloperoxidase induce less pulmonary inflammation

Query no.	Query	Response
1	The affiliations have been reordered here to reflect the order of citation – please check carefully.	
2	Sentence beginning “Biodegradation” OK as amended?	
3	Please confirm you mean “less inflammatory” here and not “fewer inflammatory”	
4	CCD expanded OK?	
5	Acknowledgments section – please expand acronyms	
6	Fig 1c,4a, please define O.D. (optical density?)	
7	Fig 3b, d left axis labels – is $10 \times 10^6$ correct? Or $1 \times 10^6$ ?	
8	Figs 3b-d, 5a – please define the error bars	
9		
10		
11		
12		
13		
14		
15		
16		
17		
18		
19		